

Tungstosilicic acid ($H_4SiW_{12}O_{40}$) Have Efficient Catalysts for Synthesis of 2,3-Dihydroxynaphthoquinone from Lawsone

N. Benferrah^{(1,2)*}, M. Hammadi⁽³⁾, H. Dokari⁽³⁾, F. Berthiol⁽⁴⁾

1) URMPE Research Unit for Materials, Processes and Environment, UMB Boumerdes, University of M'Hamed Bougara, 35000 Boumerdes, Algeria;

2) Scientific and Technical Research Center in Physical Chemical Analyses (C.R.A.P.C) 35000, Boumerdes, Algeria

3) Department of Chemistry, UMB Boumerdes, Faculty of Sciences, 35000 Boumerdes, Algeria

4) Department of Molecular Chemistry (SERCO), UMR-5250, ICMG FR-2607, University Joseph Fourier, 301 Rue de la Chimie, BP 53, Grenoble Cedex 9, 38041 France

*Corresponding author: benferrahnassima@gmail.com

ARTICLE INFO

Article History:

Received : 11/10/2016

Accepted : 10/02/2017

Key Words

Heteropolyacids ;
Without solvent ;
Room temperature ;
Lawsone ;
Catalytic system
(Pc[Co]/K10) ;
2,3-
dihydroxynaphthoquinone.

ABSTRACT/RESUME

Abstract : The Thiele–Winter reaction is of interest for synthesis of tetracetoxylaromatic precursors of hydroxynaphthoquinones. Solid acids such as Tungstosilicic acid ($H_4SiW_{12}O_{40}$) have an efficient catalyst in acetoxylation reaction of naphthoquinones without the use of organic solvent at room temperature. 1,2,3,4-Tetrahydroxynaphthalene was easily oxidized at room temperature in 2,3-Dihydroxynaphthoquinone by using (Pc[Co]/K10) and air (1 atm). We have also tested this type of reaction in 2-hydroxynaphthoquinone (Lawsone). Many naphthoquinones are natural products with interesting biological properties.

I. Introduction

The founding principles of green chemistry are mainly based on:

- The removal, if possible, of pollutant solvents that do not respect the environment. Nowadays, the use of inorganic solid acid catalysts in dry reactions (without organic solvent) offers many possibilities in the field of organic synthesis. Indeed they provide a simplification of the experimental protocols, easy recycling, and thereby easy protection of the environment.
- The improvement in the energy efficiency that beneficially affects the economy and the environment that must be considered and should be minimized by the development of synthetic methods at room temperature conditions.

One of the main problems in the chemical industry is the search for tolerable procedures for chemical production. There is a growing demand for the development of selective, efficient, and environmentally appropriate synthetic methods.


Organic solvents are not only expensive, but are often flammable, toxic, and hazardous. Generally the use of solvent is considered to be necessary in organic reactions. The hydroxynaphthoquinones [1] are well-known substances for their chemical and biologic properties [2]. The hydroxynaphthoquinones including Phthiocol [3], Lawsone [4, 5], Juglone [6, 7], and Atovaquone [8] have gained much interest due to their presence in natural products and their pharmacological properties as antitumoral, antiprotozoal, anti-inflammatory, antiviral, and antifungal [9, 10].

We have used this methodology to prepare the acetoxylation reactions of 2-hydroxynaphthoquinone acid-catalyzed by heteropolyacid $H_4SiW_{12}O_{40}$, in the absence of solvent at room temperature.

Our attention has focused on the use of metallic phthalocyanines supported in the oxidative reactions of naphthotriols prepared from the Thiele–Winter reaction in order to synthesize hydroxynaphthoquinone natural products having

antibiotic properties. The acetoxylation reaction of Lawsone with acetic anhydride (CH_3CO)₂O catalyzed by sulfuric acid H_2SO_4 [**11**, **12**] ($\text{H}_0 = -11.94$), at room temperature is slow with low yields especially in the presence of substituents on the naphthoquinone as electron donors. Sulfuric acid (H_2SO_4) was replaced by chlorozincic acid [**13**] and tetrafluoroboric acid [**1**] with low yields. To overcome this problem where the acidity of the medium thus protonation of the 2-hydroxynaphthoquinone is the decisive step, we

opted for the use of solid super acid as heterogeneous conditions in the heteropolyacid: $\text{H}_4\text{SiW}_{12}\text{O}_{40}$. In our work we are particularly interested in the synthesis of 2,3-dihydroxy-1,4-naphthoquinone (**3**). Transformation of lawsone into tetracetoxy (**2**) by the Thiele–Winter reaction. The saponification of (**2**) followed by catalytic oxidation in situ of naphthotriols is shown in (Scheme.1)

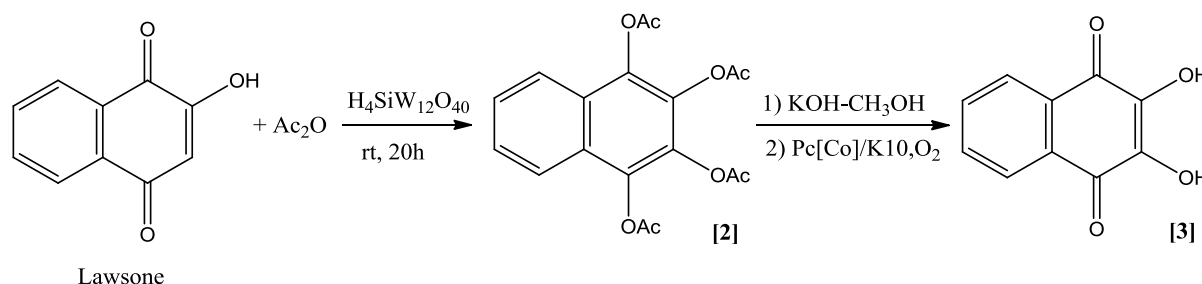

Scheme 1. Synthesis of **3** from Lawsone

II. Experimental

II.1. Materials

Melting points (m.p.) were determined with a Kofler hot apparatus and are uncorrected. Proton NMR spectra (PMR) were determined on Bruker AC 250 (250 MHz, CDCl_3 , Me₄Si). The IR spectra were recorded as KBr pellets on Perkin Elmer 16 PC FT-IR spectrometer. UV–visible spectra (λ_{max} $\log(\epsilon)$) were obtained with spectrophotometer Perkin-Elmer Lambda 15.

Microwave irradiation was carried out with a commercial microwave oven (Toshiba ER 7620) at 2,450 MHz, Mass spectra were carried out on a Nermag Riber R10; TLC analyses were performed by using Kieselgel Schleicher and Shull F 1500 Ls 254 and Merck 60F 254. The grinding of products was carried out on analytical grinder A 10 of Janke and Kenkel-IKA Labortechnik.

II.2. Methods

II.2.1 Spectroscopic characterization of lawsone (2-Hydroxy-1,4-naphthoquinone): Orange solid, yield: 79 %, m.p: 194 °C; UV-visible λ_{max} $\log(\epsilon)$ (dioxane/ H_2O) nm: 276.3 (4.48), 334.3 (3.28); IR (KBr) cm^{-1} : 3166 (ν OH), 1676 (ν C = O), 1592, 1170, 874, 668, 536; ^1H NMR (CDCl_3): δ 6.37 (s, 1H, OH); 7.26 (s, 1H, H arom.); 7.25-8.14 (m, 4H, H arom); $\text{C}_{10}\text{H}_6\text{O}_3$, calcd: H, 3.47 %; C, 68.97 %; found: H, 3.53 %; C, 68.92 %;

II.2.2 Phthalocyanine(Co) Supported on K10 (1)

a) Preparation of Montmorillonite K10 Exchanged by Co^{2+}

In a 250 ml flask, the Montmorillonite K10 (20 g) was added to a solution of metallic salt CoCl_2 (0.2 mol) dissolved in 100 ml of distilled water. The

reaction mixture was stirred for 24 h at room temperature. The suspension was washed twice with distilled water then centrifuged. The Montmorillonite exchanged by Co^{2+} was washed with methanol and re-centrifuged. The solid was dried for 24 h in vacuum then finely ground. The final product was a clear beige color.

b) Phthalocyanine Intercalated in the Montmorillonite K10

A solution of phthalonitrile (20 mmol; 2.56 g) dissolved in 20 ml of dichloromethane was added to the solid Montmorillonite K10 (5 g) exchanged with some metallic cations (Co^{2+}). After contact for 2 h, the remaining liquid was evaporated under reduced pressure. The activation of the solid under microwave irradiation (MO): p = power, t = time of irradiation) was carried out in a resonance cavity. After cooling, the solid was successively washed with water, acetone (20 ml), and then with dichloromethane (20 ml). The solid was dried under reduced pressure and the extracted with acetonitrile as a solvent using a Soxhlet for 8 h. Catalysts were characterized by FT-IR; electronic spectra of metalated phthalocyanine intercalated into Montmorillonite were very close to those observed with pure metalated phthalocyanine, but the bands were shifted.

(Pc[Co] Supported on K10) (1): microwaves irradiation Resonance Cavity. (p = 630 W, t = 10 min); Purple solid, m.p > 300 °C $\text{C}_{32}\text{H}_{16}\text{CoN}_8$; yields: 85 %, UV-visible λ_{max} $\log(\epsilon)$ / (1-chloronaphthalene) nm: 669.5 (4.42); 642.1 (3.88); 604.2 (3.78); 580.1 (3.22); IR (KBr) cm^{-1} : 1636, 1522, 1400, 1044, 870, 796, 756, 532, 525, 466.

II.2.3 Acetoxylation Reaction Under Heterogeneous Conditions (Solid Acids)

In a typical experiment, 10 mmol of Lawsone were dissolved in acetic anhydride (0.2 mol; 21.64 g). One gram of catalyst ($H_4SiW_{12}O_{40}$) was added and the mixture was stirred at room temperature. After 48 h, the products were separated by chromatography on a silica column eluted successfully with ethyl acetate/cyclohexane (10/90). The different fractions gave, respectively, a yellow solid (unreacted quinone) and a beige solid (1,2,3,4-tetracetoxynaphthalene) (2). It must be noted that traces of products of diacetylation could be detected by thin-layer chromatography (TLC).

1,2,3,4-Tetracetoxynaphthalene (2): Beige solid, yield 66 %, m.p: 140-143°C, $C_{18}H_{16}O_8$; IR (KBr) cm^{-1} : 3012 (ν CH arom.), 1760 (ν OCOCH₃), 1718; ¹H NMR (CDCl₃): δ 2.39 (s, 6H, OCOCH₃); 2.44 (s, 6H, OCOCH₃); 7.46-8.14 (m, 4H, H arom.); MS m/z (%): 360 (M⁺; 24.46), 318 (3.41), 276 (16.38), 192 (100), 146 (11.95), 105 (23.55).

II.2.4 Saponification and Oxidation In Situ

In a typical experiment, a current of air is passed through a U tube fitted with a filter flask. The tube contains the (Pc(Co)/K10 (0.1 g) in suspension in a solution of product (2) (0.6 g) dissolved in CH₃OH (20 ml) and KOH (2 g) for 6 h at room temperature. After filtration and evaporation of the methanol, the product (3) is crystallized.

2,3-Dihydroxy-1,4-naphthoquinone (3): Beige clear solid, yield: 91 %, m.p: 201 °C, $C_{10}H_6O_4$, UV-visible λ_{max} log(ε) (dioxane/H₂O) nm: 289.3 (4.77), 339.3 (3.27); IR (KBr) cm^{-1} : 3172 (ν OH), 1678 (γ C=O), 1589, 1174, 878, 536; ¹H NMR (CDCl₃): δ 6.41 (s, 1H, OH); 6.42 (s, 1H, OH); 7.31-8.11 (d, 4H, H arom).

III. Results and discussion

Thiele–Winter Reaction

The 2-hydroxynaphthoquinone (Lawsone) treated with acetic anhydride in the presence of solid acid converts into the 1,2,3,4-tetracetoxynaphthalene (2) (yield 66 %).

We have studied this reaction with strong acids. Chlorosulfonic acid (Ho = 13.80) [14-16] led to the desired product. The reaction with solid super acids shows a high Brønsted acidity.

Heteropolyacids (HPAs also called polyoxometalates) are catalysts of very great interest [17, 18]. The display has a very high Brønsted acidity close to super acids.

We decided to test three heteropolyacids $H_3PW_{12}O_{40}$ (PW), $H_4SiW_{12}O_{40}$ (SiW), and $H_3PMo_{12}O_{40}$ (PMO). The (SiW) provided the product with a yield of 66 % whereas a yield of 61 % was achieved with the (PW). It has been noticed that the (SiW) appeared a better catalyst than the (PW). This could be because of the higher ratio of the number of protons in (SiW) [19].

We have noticed that no product (3) was obtained with the $H_3PMo_{12}O_{40}$ (PMO). The reaction medium color changed from green to deep blue, proving the reduction of PMO. The result with (PMO) is not surprising owing to its high redox potential resulting from the presence of the molybdenum atom. Results of acetoxylation of Lawsone by acetic anhydride obtained from different acids catalysts are reported in Table.1.

Table 1. Acetoxylation of Lawsone at 20 °C

Catalyst	Aspect	Hammett: Ho	Experimental	M.p.(°C)	IR vester (cm^{-1})	Yield (%)
$ClSO_3H$	Liquid	-13.80	20C, 20h	149	1772	54
$H_3PW_{12}O_{40}$	Solid	-13.6	20C, 48h	149	1768	61
$H_3PMo_{12}O_{40}$	Solid	-	20C, 48h	-	-	-
$H_4SiW_{12}O_{40}$	Solid	-	20C, 48h	152	1760	66

The 1,2,3,4-tetracetoxynaphthalene (2) was easily transformed into (3) by saponification

basic and oxidation with potassium hydroxide (KOH) in methanol (CH₃OH) in the presence of


air at room temperature. The yield of 2,3-dihydroxy-1,4-naphthoquinone from (3) is good (91 %). The results obtained from the two-step sequence (tetracetoxyaromatic and

saponification-oxidation in situ) are reported in Table.2.

Table 2. Tungstosilicic acid ($H_4SiW_{12}O_{40}$) as catalyst for oxidation by molecular oxygen

1) Thiele-Winter: tetracetoxyaromatic		2) [Saponification-oxidation] in situ	

Mechanism proposed :

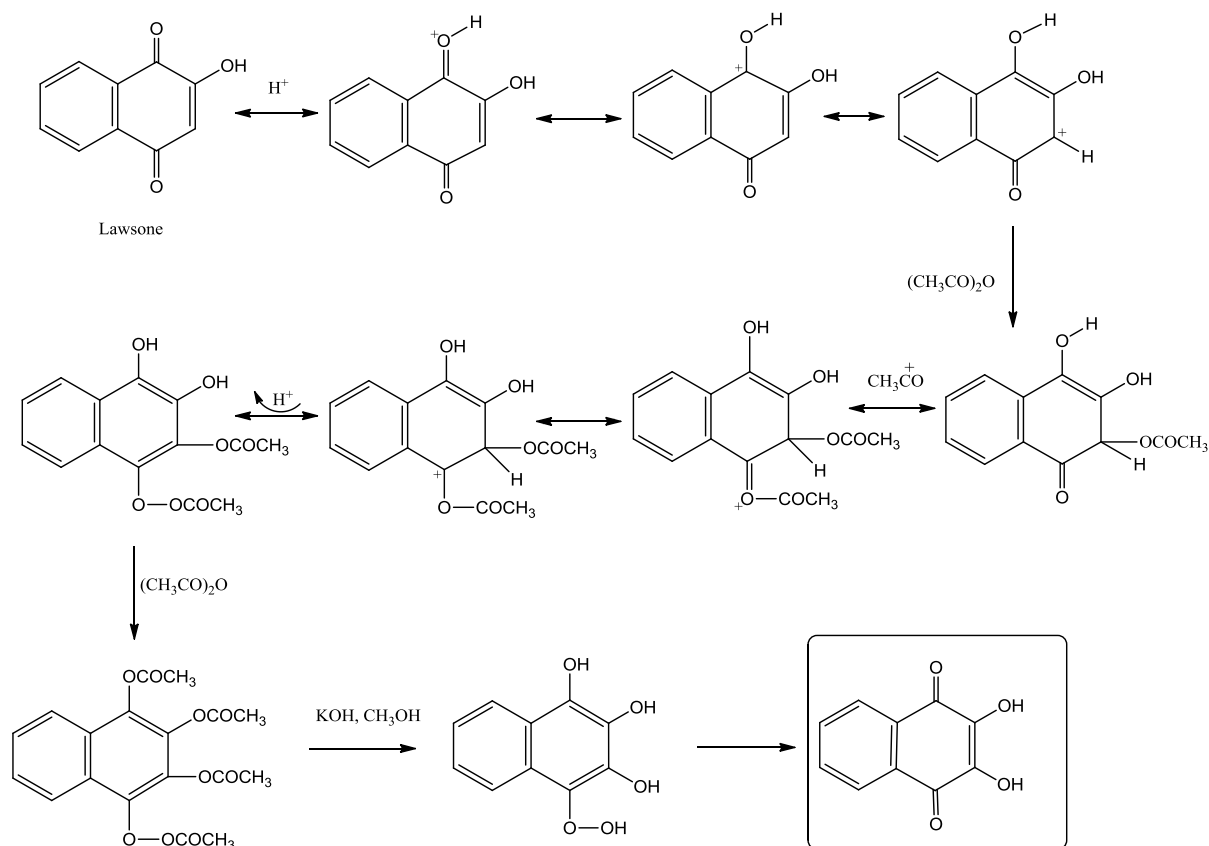

IV. Conclusion

In conclusion it appears that heteropolyacids ($H_4SiW_{12}O_{40}$) can easily catalyze the Thiele-Winter

reaction. This work represents the first example of catalysis of this reaction by solid acids. The sequence of the two steps (acetoxylation, saponification-oxidation) constitutes a new

synthesis of 2,3-dihydroxynaphthoquinones from Lawsone.

V. References

1. McOmie JFW, Blatchey JM (1972) Thiele–Winter acetoxylation of quinones. *Org React* 9:199.
2. Spyroudis S (2000) Hydroxyquinones: synthesis and reactivity. *Molecules* 5:1291.
3. Lira AM, Araujo AAS, Basilio IDJ, Santos BLL, Santana DP, Macedo RO (2007). Compatibility studies of lapachol with pharmaceutical excipients for the development of topical formulations. *Thermochim Acta* 457:1.
4. Sauriasari R, Wang DH, Takemura Y, Tsutsui K, Masuoka N, Sano K, Horita M, Wang BL, Ogino K (2007) Cytotoxicity of lawsone and cytoprotective activity of antioxidants in catalase mutant *Escherichia coli*. *Toxicology* 235(1–2):103–111.
5. Windholz M (1993) The Merck index, 12th edn. Merck, Rahway.
6. Combes R (1907) Procédé de préparation et de purification des dérivés oxyanthroquinoniques et oxynaphthoquinoniques en général, du juglonet de l'émodin en particulier. *Bull Soc Chim France* 4^e série. I, pp 800–816.
7. Soderquist CJ (1973) Juglone and allelopathy. *J Chem Educ* 50:782–783.
8. Kessl JJ, Moskalev NV, Gribble GW, Nasr M, Meshnic SR, Trumpower BL (2007) Parameters determining the relative efficacy of hydroxy-naphthoquinone inhibitors of the cytochrome bc1 complex. *Biochim Biophys Acta* 1767(4):319–326.
9. Teimouri MB, Khavasi HR (2007) One-pot three-component regioselective synthesis of linear naphtho[2,3-b]-furan-4,9-diones. *Tetrahedron* 63:10269–10275.
10. Valente C, Moreira R, Guedes RC, Iley J, Jaffar M, Douglas KT (2007) The 1,4-naphthoquinone scaffold in the design of cysteine protease inhibitors. *Bioorg Med Chem* 15(15):5340–5350.
11. Thiele J (1898) Ueber die Einwirkung von Essigsäure-anhydrid auf Chinon und auf Dibenzoylstyrol. *Ber Dtsch* 31:1247–1249.
12. Thiele J, Winter E (1900) Ueber die Einwirkung von Essigsäureanhydrid und Schwefelsäure auf Chinone. *Ann Chem* 311:341–352.
13. Burton H, Praill PFG (1952) Acylation reactions catalysed by strong acids. Part VI. A comparison of zinc chloride and perchloric acid as catalysts for the Thiele acetylation of quinines. *J Chem Soc* 755–759.
14. Hull NF, Conant JB (1927) A study of superacid solutions the use of the chloranil electrode in glacial acetic acid and the strength of certain weak bases. *J Am Chem Soc* 49:3047–3061.
15. Olah GA, Pradash GKS, Sommer J (1985) *Superacids*. Wiley, New York.
16. Olah GA (1993) *Superelectrophiles*. *Angew Chem Int Ed Engl* 32:767.
17. Izumi Y, Urabe K, Onaka M (1992) Zeolite, clay and heteropolyacid, in *organic reactions*, vol 100. VCH, Weinheim, p 120.
18. Dupont P, Lefebvre F (1996) Esterification of propanoic acid by butanol and 2-ethylhexanol catalyzed by heteropolyacids pure or supported on carbon. *J Mol Catal A Chem* 114 (1–3):299–307.
19. Izumi YK, Matsuo K, Urabe K (1983) Efficient homogenous acid catalysis of heteropoly acid and its characterisation through ether cleavage reactions. *J Mol Catal* 18:299–314.

Please cite this Article as:

Benferrah, N., Hammadi, M., Dokari, M., Berthiol, F., *Tungstosilicic acid (H₄SiW₁₂O₄₀) Have Efficient Catalysts for Synthesis of 2,3-Dihydroxynaphthoquinone from Lawsone, Algerian J. Env. Sc. Technology, 3:2 (2017) 63-67*