

# Cyanide removal from aqueous solution by oxidation with hydrogen peroxide in the presence of activated alumina-supported copper catalyst

Farid Halet<sup>1,2\*</sup>, Salima Chergui<sup>2</sup>, Farida Hamdache<sup>2</sup>, Abderrahmane Boutrif<sup>2</sup>, Abdelmalek Chergui<sup>2,3</sup>, Aissa Ould-Driss<sup>4</sup>, Lylia Boudriche<sup>5</sup>, Erwan Guénin<sup>4</sup>, Boubekeur Nadjemi<sup>2</sup> and Ahmed Reda Yeddou<sup>2</sup>

<sup>1</sup>Department of Biology, University M'Hamed Bougara Boumerdes, Avenue de l'indépendance, Boumerdes 35000, Algeria

<sup>2</sup>Laboratoire d'Etude et de Développement des Techniques de Traitement et d'Épuration des Eaux et de Gestion Environnementale – LEDTEGE, Ecole Normale Supérieure Kouba, BP 92 Vieux Kouba 16050, Algiers, Algeria

<sup>3</sup>Laboratoire des Sciences et Techniques de l'Environnement, Département Génie de l'Environnement, Ecole Nationale Polytechnique d'Alger, 10 rue Hassen Badi El Harrach Algiers, Algeria

<sup>4</sup>Laboratoire TIMR, EA4297, Centre de Recherche de Royallieu, Sorbonne Universités - Université de Technologie de Compiègne, rue du docteur Schweitzer, CS 60319, 60203 Compiègne cedex, France



<sup>5</sup>Centre de Recherche Scientifique et Technique en Analyses Physico-Chimiques, BP 384 Bou-Ismaïl, RP 42004 Tipaza, Algeria

Received: 06/12/2023, Accepted: 17/01/2024, Available online: 22/01/2024

\*to whom all correspondence should be addressed: e-mail: f.halet@univ-boumerdes.dz, haletfarid@gmail.com

<https://doi.org/10.30955/gnj.005639>

## Graphical abstract

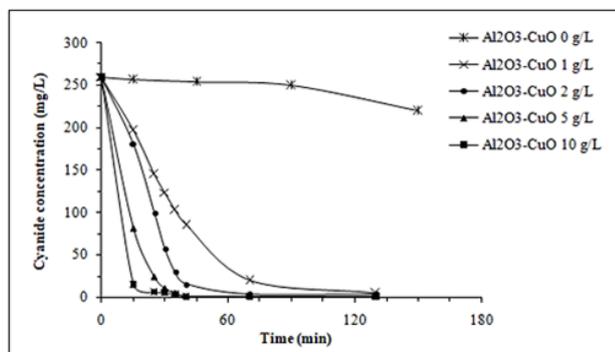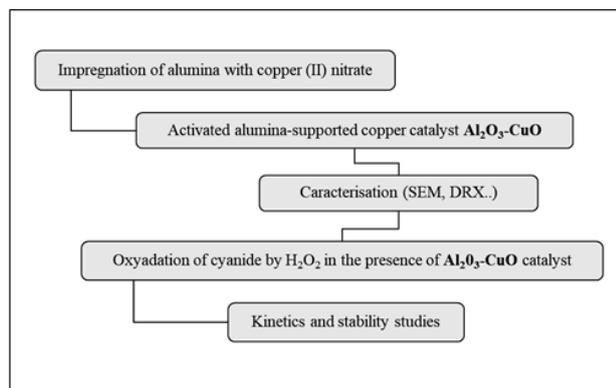

## Abstract

Cyanide compounds are widely used in some electroplating, chemical, and metallurgical industries. They are often found in their liquid discharges. This work highlights the performance of an activated alumina-supported copper catalyst in the removal of cyanide by

oxidation with hydrogen peroxide in aqueous solution. The influence of catalyst dose, initial molar ratio of hydrogen peroxide/cyanides, temperature, and catalyst reuse was studied. The activated alumina-supported copper significantly enhanced the reaction rate showing a good catalytic activity. The efficiency of cyanide elimination was increased after 30 minutes of oxidation from 48% to 98% by increasing the catalyst dose from 1 to 10 g/L. Raising the temperature from 30°C to 40°C promoted cyanide removal. The catalyst can be recycled four times and show good stability. The kinetics of cyanide oxidation was revealed to be pseudo-first-order regarding cyanides. The rate constants as well as the activation energy were determined.

**Keywords:** Cyanide; oxidation; hydrogen peroxide; catalysis; activated alumina-supported copper

## 1. 1. Introduction

Today, the industry is experiencing an increasing use of chemicals. Some products, although very useful in production or transformation processes, are considered very dangerous and end up in the discharges of the industries that use them. Cyanides are among these compounds. They are found in the liquid effluents of a large number of industries, namely chemical, metallurgical, and even food (Somboonchai & Nopharatana 2008; Kuyucak & Akcil 2013; Anupong *et al*, 2022; Costa *et al*, 2022). Cyanides can be in the form of stable metal complexes (Strong Acid Dissociable SADs), nonstable metal complexes (Weak Acid Dissociable WADs), or free cyanides (Akci 2010). The latter two forms are the most dangerous because they have the ability to release very toxic cyanide ions (Kuyucak & Akcil 2013; Uppal *et al*, 2016). The removal

of cyanides from industrial effluent can be done by different processes, like hydrogen peroxide oxidation (Yubo *et al.*, 2018; Amaouche *et al.*, 2019), Alkaline chlorination oxidation (Kuyucak & Akcil 2013; Kamrani *et al.*, 2019), electro-oxidation (Berenguer *et al.*, 2017; Dobrosz-Gomez *et al.*, 2020; Ken & Sinha 2021), ozone oxidation (Morillo Esparza *et al.*, 2019), photo-oxidation (Núñez-Salas *et al.*, 2019; Chegini *et al.*, 2020) biological oxidation (Singh & Balomajumder 2016), precipitation (Liu *et al.*, 2021) and adsorption on activated carbon (Halet *et al.*, 2015; Ravuru *et al.*, 2019; Eskandari *et al.*, 2021; Chergui *et al.*, 2022).

The hydrogen peroxide oxidation catalyzed by dissolved copper Cu (II) is currently widely used and is very effective. It allows cyanides to be oxidized to much less toxic cyanates (Knorre & Griffiths 1984; Akcil 2010). This process has the advantage of not producing dangerous by-products. However, copper is not recoverable and is itself a heavy metal that should be removed. To circumvent this, heterogeneous catalysis could be the right alternative. Indeed, much work on the elimination of pollutants by oxidation proposes to use heterogeneous catalysts based on oxides of transition metals (Hussain *et al.*, 2020; Magalhães *et al.*, 2020). These oxides can be supported on materials such as activated carbon (Ruimei *et al.*, 2018), activated alumina (Covinich *et al.*, 2016; Bousalah *et al.*, 2021), and even on natural supports (Kitis *et al.*, 2005). Following several works to improve cyanide hydrogen peroxide oxidative removal using heterogeneous catalysts (Yeddou *et al.*, 2010; Chergui *et al.*, 2015; Amaouche *et al.*, 2019; Tu *et al.*, 2019; Behnami *et al.*, 2021) we propose here to prepare a catalyst having both good stability and high efficiency. We thus suggest using activated alumina-supported copper. Activated alumina is renowned for its great surface area and surface characteristics, while copper is chosen for its catalytic performance. The study addresses the influence of different parameters such as catalyst dose, the initial molar ratio of hydrogen peroxide/cyanides, and temperature on catalyst efficacy, and studies catalyst stability.

## 2. Materials and methods

### 2.1. Reagents and analytical procedure

The chemicals employed in this study are of analytical reagent grade and are utilized as obtained without additional purification (sourced from Merck, Darmstadt, Germany, and Sigma-Aldrich, St. Louis, USA). Cyanide solutions were produced using potassium cyanide (99%). The pH of the solution was adjusted with NaOH solution (1 N) or HCl solution (1 N).

The cyanide concentration was assessed through two methods: a titrimetric approach utilizing silver nitrate, and a potentiometric method employing a cyanide-specific electrode (Orion 96-06, Boston, USA) (Baird *et al.*, 2017). pH measurement was conducted with a pH meter (HI 221, HANNA instruments). Cyanates concentration was determined by quantifying the ammonia resulting from their acid hydrolysis (1.5-2.0) through a potentiometric method (Baird *et al.*, 2017) using the ammonia-specific

electrode WTW NH 500/2. Copper ( $\text{Cu}^{2+}$ ) in the aqueous solution was analyzed using an atomic absorption spectrophotometer (Perkin Elmer, Model A Analyst 700).


### 2.2. Preparation and characterization of the activated alumina-supported copper

The catalyst support utilized in this study was neutral activated alumina obtained from Sigma-Aldrich (St. Louis, USA) with a particle size of 149-250  $\mu\text{m}$ , BET surface area of 155  $\text{m}^2/\text{g}$ , and pores volume of 0.4  $\text{cm}^3/\text{g}$ . The activated alumina-supported copper, denoted as  $\text{Al}_2\text{O}_3\text{-CuO}$ , was prepared using the pore volume impregnation method (Zhao *et al.*, 2004; Yeddou *et al.*, 2011; Shelepova *et al.*, 2017). This involved impregnating the activated alumina with an aqueous solution of copper (II) nitrate ( $\text{Cu}(\text{NO}_3)_2 \cdot 3\text{H}_2\text{O}$ ), followed by drying for 12 hours in ambient air at 50  $^\circ\text{C}$ , then at 110  $^\circ\text{C}$  for 12 hours, and finally calcination in air at 450  $^\circ\text{C}$  for 2 hours. The resulting  $\text{Al}_2\text{O}_3\text{-CuO}$  catalyst holds 5 wt.% of copper.

The analysis of  $\text{Al}_2\text{O}_3\text{-CuO}$  was performed by X-ray diffraction (XRD) (Inel cps 120, iron anti-cathode,  $k=1.936 \text{ \AA}$ ) allowing angular measurements in the range of  $2\theta = 5\text{--}125^\circ$ . The surface morphology of the activated alumina-supported copper catalysts was determined using scanning electron microscopy (SEM, Philips ESEM XL 30). The mass titration method was used for the determination of the zero-charge point (pHzc).

### 2.3. Experimental

The experiments were conducted in a double-walled glass batch reactor containing 1 liter of cyanide solution. The solution was mixed with activated alumina-supported copper ( $\text{Al}_2\text{O}_3\text{-CuO}$ ) using a magnetic stirrer at a speed that allows a homogeneous suspension of the catalyst. At different times, the residual cyanide concentration was measured. The concentration of cyanate was analyzed at the time the experiments were completed. The studied parameters were the  $\text{Al}_2\text{O}_3\text{-CuO}$  dose, the initial molar ratio of hydrogen peroxide/cyanide concentration ( $[\text{H}_2\text{O}_2]_0/[\text{CN}^-]_0$ ), and the temperature. The study of catalyst stability was evaluated by measuring its activity when reused.

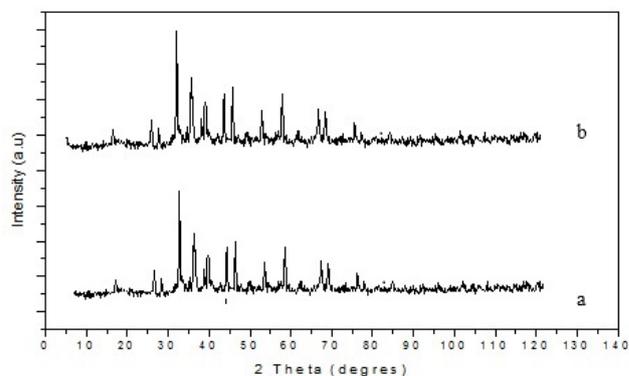

**Figure 1.** XRD spectra of (a) fresh  $\text{Al}_2\text{O}_3\text{-CuO}$ , (b)  $\text{Al}_2\text{O}_3\text{-CuO}$  (fourth use)

## 3. Results and discussion

### 3.1. Characterization of activated alumina supported-copper ( $\text{Al}_2\text{O}_3\text{-CuO}$ )

Figure 1 illustrates the X-ray diffraction spectra of Al<sub>2</sub>O<sub>3</sub>-CuO. The presence of crystalline CuO is shown in our catalysts (peaks at 2θ = 32.5°, 35.4°, 38.9°, 48.7°, 61.5°, 68.1°, and 72.3°). This crystalline structure is still present after four successive oxidation tests with no visible thinning or widening of the peak indicating good stability in time.

The scanning electron micrograph (Figure 2) of Al<sub>2</sub>O<sub>3</sub>-CuO shows the appearance of aggregate particles (probably of CuO) on the surface of the alumina. They are distributed in a homogeneous way. The pH of zero charges (pH<sub>zc</sub>) for Al<sub>2</sub>O<sub>3</sub>-CuO is found to be 6.2.

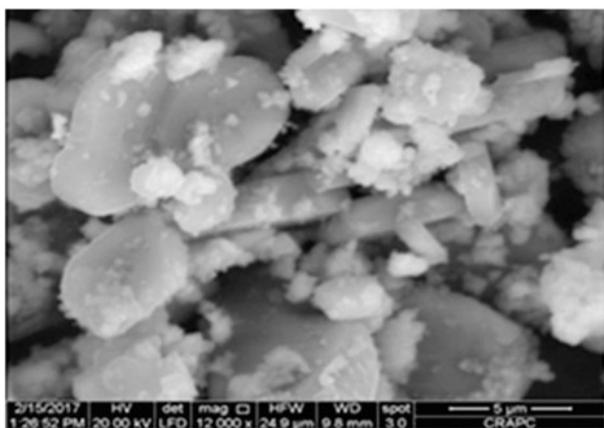


Figure 2. Scanning electron micrograph of Al<sub>2</sub>O<sub>3</sub>-CuO

3.2. Effect of activated alumina supported-copper dose (Al<sub>2</sub>O<sub>3</sub>-CuO)

The influence of the concentration of activated alumina-supported copper on the cyanide oxidation (Figure 3) was studied for doses of 0, 1, 2, 5, and 10 g/L, for an initial cyanide concentration of 10 mM (260 mg/L), and for an initial molar ratio [H<sub>2</sub>O<sub>2</sub>]<sub>0</sub>/[CN<sup>-</sup>]<sub>0</sub> equal to 3. Temperature and pH were maintained at 20°C and 11, respectively. In the case without an Al<sub>2</sub>O<sub>3</sub>-CuO catalyst (Figure 3), cyanide oxidation is very slow. The presence of Al<sub>2</sub>O<sub>3</sub>-CuO significantly improves the kinetics and efficiency of the oxidation, especially at high doses. Indeed, after 30 minutes, cyanide concentrations of 255, 124, 58, 11, and 5 mg/L (elimination percentages of 2, 52, 78, 96, and 98%) are reached for the respective doses of Al<sub>2</sub>O<sub>3</sub>-CuO of 0, 1, 2, 5 and, 10 g/L. As reported in the literature (Bradou *et al*, 2010; Covinich *et al*, 2016; Bousalah *et al*, 2021 ; Meng *et al*, 2021) copper oxide CuO was able to decompose the hydrogen peroxide and to produce highly reactive hydroxyl radicals that oxidize the pollutant. Therefore, it can be hypothesized that the activated alumina-supported copper catalyst produces hydroxyl radicals according to reaction equation 1 which allows for the oxidation reaction of cyanide ions.

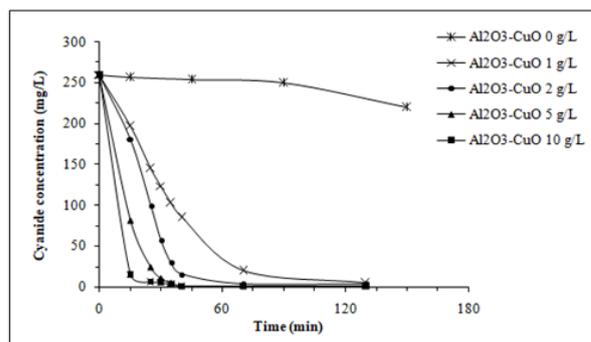



Figure 3. Effect of Al<sub>2</sub>O<sub>3</sub>-CuO dose on cyanide removal by peroxide hydrogen oxidation: [H<sub>2</sub>O<sub>2</sub>]<sub>0</sub>/[CN<sup>-</sup>]<sub>0</sub> = 3, CN<sub>0</sub> = 260 mg/L, T = 20 °C, pH = 11.0

3.3. Initial concentration effect of hydrogen peroxide

The effect of hydrogen peroxide dose was studied for initial molar ratios [H<sub>2</sub>O<sub>2</sub>]<sub>0</sub>/[CN<sup>-</sup>]<sub>0</sub> varying from 1.5 to 20. The initial cyanide concentration was 10 mM (260 mg/L), the catalyst dose was 3 g/L, and the temperature was fixed at 20° C. Figure 4 showed that after 30 minutes, the cyanide concentrations of 30, 20, 15, and 11 mg/L were reached for the molar ratios of 1.5, 5, 10 and 20, respectively. This corresponds to percentages of elimination of 88, 92, 94, and 96 %, respectively. It could be pointed out that for the range of hydrogen peroxide initial concentration studied, the cyanide elimination rate was high, thus showing the beneficial contribution of the catalyst even for low molar ratios, that is to say with molar ratios close to the stoichiometry of oxidation reaction. This is because, at a molar ratio of 1.5, the catalyst can produce enough OH<sup>•</sup> radicals to oxidize the cyanide ions. The presence of the catalyst significantly improved the rate and yield of cyanide oxidation. Yeddou *et al.* (2010) studied the removal of cyanides by hydrogen peroxide without, under the same conditions as the present work, they found the oxidation kinetics to be slow and they obtained an 80% of cyanide elimination for an initial molar ratio [H<sub>2</sub>O<sub>2</sub>]<sub>0</sub>/[CN<sup>-</sup>]<sub>0</sub> of 20 after 8 hours.


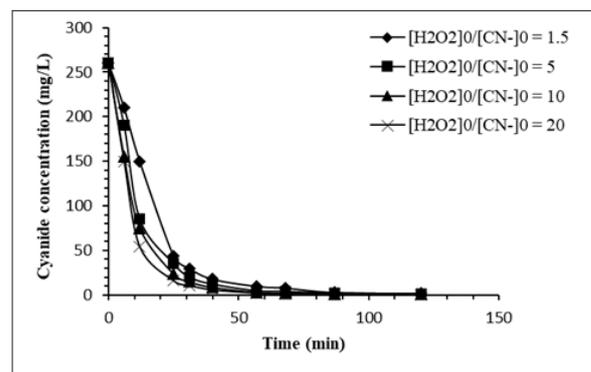


Figure 4. Effect of initial molar ratio [H<sub>2</sub>O<sub>2</sub>]<sub>0</sub>/[CN<sup>-</sup>]<sub>0</sub> on cyanide removal by peroxide hydrogen oxidation: Al<sub>2</sub>O<sub>3</sub>-CuO (3 g/L), CN<sub>0</sub> = 260 mg/L, T = 20 °C, pH = 11.0


3.4. Effect of temperature

The influence of temperature on the cyanides oxidation by hydrogen peroxide catalyzed by Al<sub>2</sub>O<sub>3</sub>-CuO was performed for 20, 30, and 40° C. The initial cyanide concentration ions were 10 mM (260 mg / L), the pH was maintained at 11.0,

the initial molar ratio  $[H_2O_2]_0/[CN^-]_0$  was equal to 3 and the dose of  $Al_2O_3-CuO$  was 3g/L. An improvement in yield and kinetics is observed (Figure 5) with increasing temperature. Indeed, after fifteen minutes removal rates of 62, 85, and 92% are achieved for temperatures of 20, 30, and 40 °C, respectively.

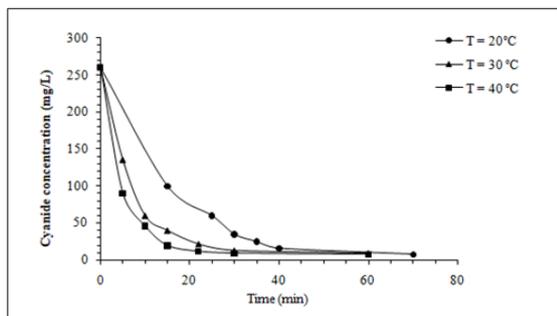

**Figure 5.** Effect of temperature on cyanide removal by peroxide hydrogen oxidation:  $[H_2O_2]_0/[CN^-]_0 = 3$ ,  $Al_2O_3-CuO$  (1 g/L),  $CN^-_0 = 260$  mg/L,  $pH = 11.0$

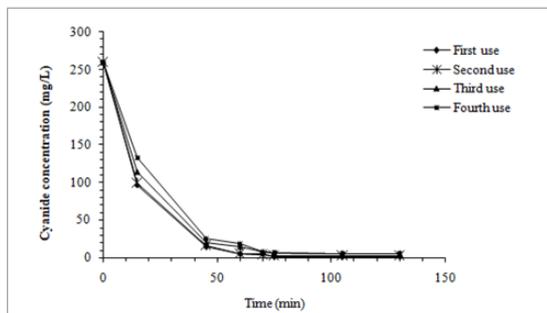

**Figure 6.** Cyanide removal by peroxide hydrogen oxidation: reuse of  $Al_2O_3-CuO$  (3 g/L),  $[H_2O_2]_0/[CN^-]_0 = 3$ ,  $CN^-_0 = 260$  mg/L,  $T = 20$  °C,  $pH = 11.0$

### 3.5. Reuse of catalyst

The stability of  $Al_2O_3-CuO$  was studied by the reuse of the sample for four successive times. Before each use, the

sample was washed with deionized water and dried at 60 °C for a few hours. The results (Figure 6) showed no major loss of activity between the first and the fourth use, indeed, after sixty minutes, the cyanide elimination yield was 98 and 93 %, respectively. The identical XRD patterns (Figure 1) for fresh under-reused reused four successive times catalyst confirmed the catalytic stability.

### 3.6 Kinetics of cyanide oxidation and determination of the activation energy

Kinetics of cyanide elimination in the presence of  $Al_2O_3-CuO$ , for different doses, were studied using the pseudo-first-order (Eq.2) and the pseudo-second-order (Eq. 3) models with regard to cyanide:

Pseudo-first order model

$$-\frac{dC}{dt} = k_{app}C \quad (2)$$

Pseudo-second order model

$$-\frac{dC}{dt} = k_{app}C^2 \quad (3)$$

Where  $C_0$ ,  $C$ , and  $K_{app}$  are the initial cyanide concentration, cyanide concentration at time  $t$ , and apparent rate constant, respectively.

Plotting the curves representing  $\ln \frac{C_0}{C}$  and  $\left(\frac{1}{C} - \frac{1}{C_0}\right)$  versus time (figures not shown) showed that the cyanide oxidation kinetics data are fitted well by the pseudo-first-order model with highly determination coefficients  $R^2$  values. The values of the apparent kinetic constants as well as the coefficients of determination  $R^2$  for each model are given in Table 1. It is noted that the  $K_{app}$  values calculated under different conditions increase significantly with the presence of activated alumina-supported copper, supporting its role as a catalyst.

**Table 1.** Kinetic model parameters for cyanide removal in oxidation by hydrogen peroxide,  $pH = 11.0$ ,  $[CN^-]_0 = 10$  mM (260 mg/L)

$Al_2O_3-CuO$ dose (g/L)	Initial molar ratio $[H_2O_2]_0/[CN^-]_0$	Temperature (°C)	Pseudo-first-order		Pseudo-second-order	
			$K_{app}(\text{min}^{-1})$	$R^2$	$K_{app}(\text{L.mmol}^{-1}.\text{min}^{-1})$	$R^2$
0	3	20	0.0005	0.960	0.0001	0.614
1	3	20	0.031	0.928	0.004	0.882
2	3	20	0.058	0.934	0.023	0.555
5	3	20	0.117	0.913	0.094	0.614
10	3	20	0.143	0.932	0.571	0.341
3	3	20	0.067	0.989	0.027	0.893
3	3	30	0.109	0.953	0.053	0.912
3	3	40	0.155	0.954	0.087	0.954
3	1.5	20	0.054	0.957	0.080	0.815
3	5	20	0.069	0.962	0.122	0.883
3	10	20	0.078	0.960	0.184	0.772
3	20	20	0.093	0.961	0.275	0.865


The activation energy of the cyanide elimination by hydrogen peroxide catalyzed with  $Al_2O_3-CuO$  is determined from the linearized Arrhenius equation (Eq.4)

$$\ln k_{app} = \ln K_0 - E_a/RT \quad (4)$$

Where  $K_0$  is the pre-exponential factor and  $E_a$  is the apparent activation energy (kJ/mol).

The apparent activation energy value is determined from the plot of  $\ln K_{app}$  versus  $1/T$  (Figure 7). It is 32.36 kJ/mol for cyanide oxidation in the presence of 3 g/L  $Al_2O_3-CuO$ . In a previously reported study, Yeddou et al. (2010) found values of 82.7 and 46.2kJ/mol in the absence of a catalyst and the presence of 10 g/L of activated carbon,

respectively. Chergui et al. (2015) reported a value of 55.7 kJ/mol with 10 g/L of alumina ( $\text{Al}_2\text{O}_3$ ). Amaouche et al. (2019), with similar working conditions, found a value of 32.2 kJ/mol by using copper oxide CuO (1 g/L) as a catalyst. The activated alumina-supported copper  $\text{Al}_2\text{O}_3\text{-CuO}$ , with a dose of 3 g/L, significantly reduced the value of activation energy, demonstrating its role as a catalyst.

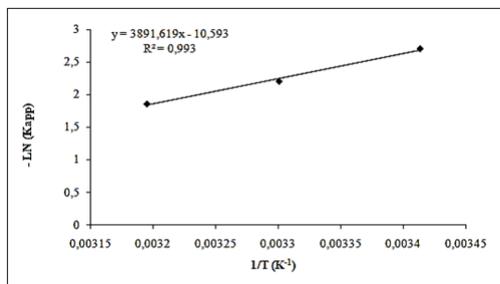

**Figure 7.** Validation of the Arrhenius law for cyanide removal in the presence of  $\text{Al}_2\text{O}_3\text{-CuO}$ :  $[\text{H}_2\text{O}_2]_0/[\text{CN}^-]_0 = 3$ ,  $\text{Al}_2\text{O}_3\text{-CuO}$  (3 g/L),  $\text{CN}^- = 260$  mg/L,  $\text{pH} = 11.0$

#### 4. Conclusion

This study consists of the oxidation of cyanides by hydrogen peroxide in the presence of the activated alumina-supported copper  $\text{Al}_2\text{O}_3\text{-CuO}$  as the catalyst, prepared by the impregnation method. The characterization of  $\text{Al}_2\text{O}_3\text{-CuO}$  shows the presence of copper oxide CuO on the surface of the catalyst. The alumina-supported copper considerably enhanced the reaction rate indicating good catalytic activity. The rate of cyanide removal is improved by increasing the catalyst dose, initial hydrogen peroxide concentration, and temperature. In almost all cases, over 90% of the cyanides are removed within 30 minutes. Good stability was observed after four consecutive reuses of the catalyst. The kinetic study showed that the oxidation of cyanides with hydrogen peroxide catalyzed by  $\text{Al}_2\text{O}_3\text{-CuO}$  is of pseudo-first order.

The benefit of the proposed process is that it avoids the use of soluble catalysts, whose disposal after treatment can be problematic. In another aspect, this process allows for rapid cyanide removal kinetics and, at the same time, only consumes hydrogen peroxide as a chemical. Good cyanide removal rates can be achieved even with lower initial molar ratios  $[\text{H}_2\text{O}_2]_0/[\text{CN}^-]_0$ .

#### Acknowledgments

This work was supported by the Ministry for Higher Education and the scientific research of Algeria (Project PRFU No. B00L01EN160220180001).

#### References

- Akcil A. (2010). A New Global Approach of Cyanide Management: International Cyanide Management Code for the Manufacture, Transport, and Use of Cyanide in the Production of Gold. *Mineral Processing and Extractive Metallurgy Review*, **31**, 135–149. <https://doi.org/10.1080/08827501003727022>
- Amaouche H., Chergui S., Halet F., Yeddou A.R., Chergui A., Nadjemi B. and Ould-Driss A. (2019). Removal of cyanide in aqueous solution by oxidation with hydrogen peroxide catalysed by copper oxide, *Water Science and Technology*, **1**, 126–133. <https://doi.org/10.2166/wst.2019.254>
- Anupong W., Jutamas K., On-uma R., Sabour A., Alshiekhe M., Karuppusamy I., Lan Chi N.T. and Pugazhendhi A. (2022). A Sustainable bioremediation approach to treat the sago industry effluents and evaluate the possibility of yielded biomass as a single cell protein (SCP) using cyanide tolerant *Streptomyces tritici* D5, *Chemosphere*, **304**, 135248. <https://doi.org/10.1016/j.chemosphere.2022.135248>
- Baird R., Eaton A. and Rice E. (2017). Standard Methods for the Examination of Water and Wastewater. twenty third edition, American Public Health Association, American Water Works Association, Water Environment Federation, Washington D.C.
- Behnami A., Croué J.P., Aghayani E. and Pourakbar M. (2021). A catalytic ozonation process using  $\text{MgO}$ /persulfate for degradation of cyanide in industrial wastewater: mechanistic interpretation, kinetics and by-products. *RSC Advances*, **11**, 36965–36977. <https://doi.org/10.1039/D1RA07789A>
- Berenguer R., La Rosa-Toro A., Quijada C. and Morallón E. (2017). Electrocatalytic oxidation of cyanide on copper-doped cobalt oxide electrodes. *Applied Catalysis B: Environmental*, **207**, 286–296. <https://doi.org/10.1016/j.apcatb.2017.01.078>
- Bousalah D., Yeddou A.R., Hachemi M., Chergui A. and Nadjemi B. (2021). Oxidation of azo dye carmoisine (E122) in aqueous solution by heterogeneous catalyst  $\text{CuO}/\text{Al}_2\text{O}_3$  system, *Environmental Engineering and Management Journal*, **20**, 167–175. <https://doi.org/10.30638/eemj.2021.017>
- Bradu C., Frunza L., Mihalche N., Avramescu S.M., Neață M. and Udrea I. (2010). Removal of Reactive Black 5 azo dye from aqueous solutions by catalytic oxidation using  $\text{CuO}/\text{Al}_2\text{O}_3$  and  $\text{NiO}/\text{Al}_2\text{O}_3$  Author links open overlay panel, *Applied Catalysis B: Environmental*, **96**, 548–556. <https://doi.org/10.1016/j.apcatb.2010.03.019>
- Chegini Z.G., Hassani A.H., Torabian A. and Borghei S.M. (2020). Comparing the efficacy of catalytic ozonation and photocatalytic degradation of cyanide in industrial wastewater using  $\text{ACF-TiO}_2$ : catalyst characterisation, degradation kinetics, and degradation mechanism, *International Journal of Environmental Analytical Chemistry*, **102**, 3023–3042. <https://doi.org/10.1080/03067319.2020.1762874>
- Chergui S., Yeddou A.R., Chergui A., Halet F., Amaouche H., Nadjemi B. and Ould-Driss A. (2015). Removal of cyanide in aqueous solution by oxidation with hydrogen peroxide in presence of activated alumina, *Toxicological & Environmental Chemistry*, **97**, 1289–1295. <https://doi.org/10.1080/02772248.2015.1093129>
- Chergui S., Yeddou A.R., Chergui A., Halet F., Nadjemi B. and Ould-Driss A. (2022). Removal of Cyanide from Aqueous Solutions by Biosorption onto Sorghum Stems: Kinetic, Equilibrium, and Thermodynamic Studies, *Journal of Hazardous, Toxic and Radioactive Waste*, **26**, 1–8. [https://doi.org/10.1061/\(ASCE\)HZ.2153-5515.0000647](https://doi.org/10.1061/(ASCE)HZ.2153-5515.0000647)
- Costa R.C., Ramos M.D.N., Fleck L., Gomes S.D. and Aguiar A. (2022). Critical analysis and predictive models using the physicochemical characteristics of cassava processing wastewater generated in Brazil, *Journal of Water Process Engineering*, **47**, 102629. <https://doi.org/10.1016/j.jwpe.2022.102629>
- Covinich L.G., Massa P., Fenoglio R.J. and Area M.C. (2016). Oxidation of hazardous compounds by heterogeneous

- catalysis based on Cu/Al<sub>2</sub>O<sub>3</sub> system in Fenton-type reactions, *Critical Reviews in Environmental Science and Technology*, **46**, 1745–1781. <https://doi.org/10.1080/10643389.2016.1267449>
- Dobrosz-Gomez I., García M.A.G., Gáviria G.H. and Gilpavas E. (2020). Mineralization of cyanide originating from gold leaching effluent using electro-oxidation: multi-objective optimization and kinetic study, *Journal of Applied Electrochemistry*, **50**, 217–230. <https://doi.org/10.1007/s10800-019-01392-1>
- Eskandari P., Farhadian M., Solaimany Nazar A. and Goshadrou A. (2021). Cyanide adsorption on activated carbon impregnated with ZnO, Fe<sub>2</sub>O<sub>3</sub>, TiO<sub>2</sub> nanometal oxides: a comparative study, *International Journal of Environmental Science and Technology*, **18**, 297–316. <https://doi.org/10.1007/s13762-020-02791-0>
- Halet F., Yeddou A.R., Chergui A., Chergui S., Nadjemi B. and Ould-Driss A. (2015). Removal of Cyanide from Aqueous Solutions by Adsorption on Activated Carbon Prepared from Lignocellulosic By-products, *Journal of Dispersion Science and Technology*, **36**, 1736–1741. <https://doi.org/10.1080/01932691.2015.1005311>
- Hussain S., Eleonora A., Sara B., Michele M., Vito G., Igino C., Luciano Z., Alessandro T. and Goi D. (2020). Enhanced ibuprofen removal by heterogeneous-Fenton process over Cu/ZrO<sub>2</sub> and Fe/ZrO<sub>2</sub> catalysts, *Journal of Environmental Chemistry Engineering*, **8**, 103586. <https://doi.org/10.1016/j.jece.2019.103586>
- Kamrani M.S., Seifpanahi-Shabani K., Seyed-Hakimi A., Agarwa G.A.M., Al Sh. and Gupta V.K. (2019). Degradation of cyanide from gold processing effluent by H<sub>2</sub>O<sub>2</sub>, NaClO and Ca(ClO)<sub>2</sub> combined with sequential catalytic process. *Bulgarian Chemical Communications*, **51**, 384–393. <https://doi.org/10.34049/bcc.51.3.5052>
- Ken D.S. and Sinha A. (2021). Dimensionally stable anode (Ti/RuO<sub>2</sub>) mediated electro-oxidation and multi-response optimization study for remediation of coke-oven wastewater, *Journal of Environmental Chemical Engineering*, **9**, 105025. <https://doi.org/10.1016/j.jece.2021.105025>
- Kitis M., Karakaya E., Yigit N., Civelekoglu G. and Akcil A. (2005). Heterogeneous catalytic degradation of cyanide using copper-impregnated pumice and hydrogen peroxide, *Water Research*, **39**, 1652–1662. <https://doi.org/10.1016/j.watres.2005.01.027>
- Knorre H. and Griffiths A. (1984). Cyanide Detoxification with Hydrogen Peroxide Using, *Proceedings of the Cyanide and the Environment Conference*, Tucson, Arizona.
- Kuyucak N. and Akcil A. (2013). Cyanide and removal options from effluents in gold mining and metallurgical processes, *Minerals Engineering*, **50–51**, 13–29. <https://doi.org/10.1016/j.mineng.2013.05.027>
- Liu Q., Zhang M., Cao Y., Peng B. and Barvor J.B. (2021). Zinc cyanide removal by precipitation with quaternary ammonium salts, *Separation and Purification Technology*, **274**, 119057. <https://doi.org/10.1016/j.seppur.2021.119057>
- Magalhães V.M., Mendes G.P., Costa-filho J.D.B., Cohen R., Partiti C.S., Vianna M.M.G.R. and Chivone-Filho O. (2020). Clay-based catalyst synthesized for chemical oxidation of phenanthrene contaminated soil using hydrogen peroxide and persulfate, *Journal of Environmental Chemical Engineering*, **8**(2), 103568. <https://doi.org/10.1016/j.jece.2019.103568>
- Meng G., Liu B., Sun M., Miao Q., Ding S., Zhang J. and Liu Z. (2021). Sludge-based activated carbon catalyzed H<sub>2</sub>O<sub>2</sub> oxidation of reactive azo dyes, *Environmental Technology*, **42**, 682–693. <https://doi.org/10.1080/09593330.2019.1643409>
- Morillo Esparza J., Cevallos Cueva N., Sandoval Pauker C., Vargas Jentzsch P. and Muñoz Bisesti F. (2019). Combined treatment using ozone for cyanide removal from wastewater: A comparison, *La Revista Internacional de Contaminación Ambiental*, **35**, 459–467. <https://doi.org/10.20937/RICA.2019.35.02.16>
- Núñez-Salas R.E., Hernández-Ramírez A., Hinojosa-Reyes L., Guzmán-Mar J. L., Villanueva-Rodríguez M. and Maya-Treviño M.D.L. (2019). Cyanide degradation in aqueous solution by heterogeneous photocatalysis using boron-doped zinc oxide. *Catalysis Today*, **328**, 202–209. <https://doi.org/10.1016/j.cattod.2018.11.061>
- Ravuru S.S., Jana A. and De S. (2019). Synthesis of NiAl-layered double hydroxide with nitrate intercalation: Application in cyanide removal from steel industry effluent. *Journal of Hazardous Materials*, **375**, 791–800. <https://doi.org/10.1016/j.jhazmat.2019.03.122>
- Ruimei F., Haibao H., Jian J., Miao H., Qiuyu F., Yujie Z. and Leung D.Y.C. (2018). Efficient MnOx supported on coconut shell activated carbon for catalytic oxidation of indoor formaldehyde at room temperature, *Chemical Engineering Journal*, **334**, 2050–2057. <https://doi.org/10.1016/j.cej.2017.11.176>
- Shelepova E.V., Vedyagin A.A., Ilna LY., Nizovskii A.I. and Tsyrlunikov P.G. (2017). Synthesis of carbon-supported copper catalyst and its catalytic performance in methanol dehydrogenation, *Applied Surface Science*, **409**, 291–295. <https://doi.org/10.1016/j.apsusc.2017.02.220>
- Singh N. and Balomajumder C. (2016). Batch growth kinetic studies for elimination of phenol and cyanide using mixed microbial culture. *Journal of Water Process Engineering*, **11**, 130–137. <https://doi.org/10.1016/j.jwpe.2016.04.006>
- Somboonchai W. and Nopharatana M. (2008). Kinetics of cyanide oxidation by ozone in cassava starch production process, *Journal of Food Engineering*, **84**, 563–568. <https://doi.org/10.1016/j.jfoodeng.2007.06.015>
- Tu Y., Wei P.H.L., Zhang X., Yu B., Qian P. and Ye S. (2019). Removal of cyanide adsorbed on pyrite by H<sub>2</sub>O<sub>2</sub> oxidation under alkaline conditions, *Journal of Environmental Sciences*, **78**, 287–292. <https://doi.org/10.1016/j.jes.2018.10.013>
- Uppal H., Tripathy S., Chawla S., Sharma B., Dalai M., Singh S. and Singh N. (2016). Study of cyanide removal from contaminated water using zinc peroxide nanomaterial. *Journal of Environmental Sciences*, **55**, 76–85. <https://doi.org/10.1016/j.jes.2016.07.011>
- Yeddou A.R., Chergui S., Chergui A., Halet F., Hamza A., Nadjemi B. and Belkouch J. (2011). Removal of cyanide in aqueous solution by oxidation with hydrogen peroxide in presence of copper-impregnated activated carbon, *Minerals Engineering*, **24**, 788–793. <https://doi.org/10.1016/j.mineng.2011.02.012>

- Yeddou A.R., Nadjemi B., Halet F., Ould-Dris A. and Capart R. (2010). Removal of cyanide in aqueous solution by oxidation with hydrogen peroxide in presence of activated carbon prepared from olive stones. *Minerals Engineering*, **23**, 32–39. <https://doi.org/10.1016/j.mineng.2009.09.009>
- Yubo T., Peiwei H., Lianqi W., Xiaomeng Z., Bo Y., Peng Q. and Shufeng Y. (2018). Removal of cyanide adsorbed on pyrite by H<sub>2</sub>O<sub>2</sub> oxidation under alkaline conditions, *Journal of Environmental Sciences (China)*, **78**, 287–292. <https://doi.org/10.1016/j.jes.2018.10.013>
- Zhao J., Liu Z. and Sun D. (2004). TPO–TPD study of an activated carbon-supported copper catalyst sorbent used for catalytic dry oxidation of phenol, *Journal of Catalysis*, **227**, 297–303. <https://doi.org/10.1016/j.jcat.2004.07.020>